

Hydroxyl accessibility in wood by deuterium exchange and ATR-FTIR spectroscopy: methodological uncertainties

Journal Article**Author(s):**

Tarmian, Asghar; Burgert, Ingo; Thybring, Emil E.

Publication date:

2017-07

Permanent link:

<https://doi.org/10.3929/ethz-b-000191313>


Rights / license:

[In Copyright - Non-Commercial Use Permitted](#)

Originally published in:

Wood Science and Technology 51(4), <https://doi.org/10.1007/s00226-017-0922-9>

Hydroxyl accessibility in wood by deuterium exchange and ATR-FTIR spectroscopy: methodological uncertainties

Asghar Tarmian¹ · Ingo Burgert^{2,3} · Emil Engelund Thybring^{2,3,4} 

Received: 9 September 2016 / Published online: 13 May 2017
© Springer-Verlag Berlin Heidelberg 2017

Abstract The accessibility of wood hydroxyls to water is commonly studied by infrared spectroscopy after deuteration where water-interacting hydroxyls have their H exchanged for D. In this study, the hydroxyl accessibility is determined with ATR-FTIR spectroscopy after deuteration of specimens with liquid D₂O. Several factors are examined to reveal the uncertainties involved in the accessibility determination. Despite the fact that specimens were able to interact with water vapour after deuteration and drying, producing a freshly cut surface just before measurement limited the effect of re-exchange of hydroxyls and gave for most batches reproducible results.

Introduction

The hygroscopicity of wood is a result of the capability of its chemical constituents to interact with water and form hydrogen bonds (H-bonds). A common way of investigating the accessibility of functional groups interacting with water is by deuteration (Altaner et al. 2006; Chow 1972; Fackler and Schwanninger 2011; Fernandes et al. 2011; Kontturi and Vuorinen 2009; Rautkari et al. 2013; Suchy 2011; Suchy et al. 2010a, b; Taniguchi et al. 1966, 1978; Thybring et al. 2017),

✉ Emil Engelund Thybring
eet@ign.ku.dk

- ¹ Faculty of Natural Resources, Department of Wood and Paper Science and Technology, University of Tehran, Tehran, Iran
- ² Department of Civil, Environmental and Geomatic Engineering (D-BAUG), Institute for Building Materials, Wood Materials Science Group, ETH Zürich, Zurich, Switzerland
- ³ Applied Wood Materials, EMPA, Dübendorf, Switzerland
- ⁴ Department of Geosciences and Natural Resource Management, University of Copenhagen, Frederiksberg, Denmark

whereby exposure to vast amounts of heavy water (deuterium oxide, D_2O) causes an H-to-D exchange of all accessible functional groups capable of forming H-bonds with the water (Englander et al. 1972). The result of the exchange can afterwards be measured either gravimetrically as an increase in dry mass or spectroscopically by significant changes ($\Delta\omega$ around 1000, 900, and 800 cm^{-1} for O–H, N–H and C–H stretching vibrations, respectively, after deuteration) in vibrational frequency of exchanged groups (Gold and Satchell 1955). The latter technique is in focus in the current study which investigates uncertainties in the spectroscopic determination of water accessibility to functional groups in untreated wood.

The main functional groups within wood cell walls interacting with water are hydroxyls. This is seen by infrared spectroscopy after deuteration where only deuterated O–H stretching vibrations are seen, whereas C–H stretching vibrations remain unchanged and no deuterated C–H vibrations can be found (Hofstetter et al. 2006; Mann and Marrinan 1956a; Schmidt et al. 2006; Taniguchi et al. 1966; Watanabe et al. 2006). Therefore, by focusing on the OD and OH stretching peaks and assuming that Beer's law holds, the relative hydroxyl accessibility can be determined as the ratio of areas of OD to OD + OH (Suchy et al. 2010b; Taniguchi et al. 1966) or alternatively by the ratio of weighted intensities of OH and OD peaks (Mann and Marrinan 1956b; Sepall and Mason 1961). The hydroxyl accessibility for wood is less than 100% as a large fraction of hydroxyl are confined within the compact, aggregated cellulose microfibrils and are inaccessible to water under normal conditions (Hofstetter et al. 2006; Salmén and Bergström 2009). This is evident from previous experimental studies of spectroscopically determined hydroxyl accessibility for various wood species, see Table 1. However, the true relative hydroxyl accessibility can be expected to differ from the experimentally derived result because of differences in specific vibrational intensity of OH and OD. Thus, it is not necessarily true that a given concentration of hydroxyls has the same vibrational intensity after full deuteration (Crawford 1952; Mann and Marrinan 1956b). For instance, cellulose and starch hydroxyl stretching vibrations were found to be about 10% more intense after deuteration (Mann and Marrinan 1956b; Nara et al. 1981), while the intensity is theoretically expected to be lower (Crawford 1952; Swenson 1965) as reported for wood with 10% lower intensity (Chow 1972)

Table 1 Relative hydroxyl accessibility determined spectroscopically after deuteration

Wood species	Hydroxyl accessibility [%]	References
Japanese red pine	42	Taniguchi et al. (1966)
Norway spruce	36	Fackler and Schwanninger (2011)
Norway spruce	40–44	Thybring et al. (2017)
Sitka spruce	43	Altaner et al. (2006)
Sitka spruce	45	Fernandes et al. (2011)
Douglas fir	24–45	Chow (1972)
Japanese cypress	47	Taniguchi et al. (1966)

and as seen for liquid water, where the hydroxyl stretching vibration intensity is 29% lower for deuterated water (Venyaminov and Prendergast 1997). While the previous results suggest a higher true value for the experimentally determined hydroxyl accessibility, the latter result suggests a lower true value. Until this issue has been resolved for lignocellulosic materials, it remains uncertain whether the spectroscopic method can yield quantitative results for wood.

In this study, it is investigated how the handling of dry, deuterated wood specimens under laboratory conditions affects the spectroscopically determined hydroxyl accessibility.

Materials and methods

Material

Wood blocks of beech (*Fagus sylvatica* L.), Norway spruce (*Picea abies* L.) and Scots pine sapwood and heartwood (*Pinus sylvestris* L.), from trees grown in Switzerland, were cut with a sharp razor blade into specimens of dimensions $15 \times 10 \times 3 \text{ mm}^3$ ($L \times R \times T$). Furthermore, Norway spruce specimens were also produced with dimensions $15 \times 10 \times 1$, $15 \times 10 \times 10^3$ and $30 \times 10 \times 3 \text{ mm}^3$ ($L \times R \times T$) to investigate the effect of specimen thickness and length. All batches contained seven replicates except for those two, related to specimen length which only contained three replicates.

Deuteration in liquid D₂O

Specimens were initially dried under vacuum (60 °C, 0 mbar, 24 h) followed by vacuum impregnation with D₂O. The latter was done by evacuating a reaction flask containing the specimens for 30 min and then injecting with a syringe through a rubber cork 40 mL liquid D₂O (99.9 atom% D, Sigma-Aldrich ½ GmbH, Buchs, Switzerland) per about 3.15 cm³ (about 1.2–1.5 g) wood under continuous vacuum pumping. Given that wood contains roughly 7–9 mmol hydroxyls per gram wood (Phuong et al. 2007; Popescu et al. 2014; Sumi et al. 1964; Thybring et al. 2017), the ratio of hydroxyls to deuterium supplied by liquid D₂O is around 1:500. Hereafter, the specimens were left at saturated vapour pressure for 60 min before atmospheric pressure was re-established with dry nitrogen gas. After 120 min under these conditions, the liquid D₂O was exchanged with a fresh batch of 40 mL D₂O, the reaction flask flushed with dry nitrogen gas and closed for overnight deuteration (24 h in total). Finally, the specimens were dried in vacuum (60 °C, 0 mbar, 24 h), after which the atmospheric pressure was re-established using dry nitrogen gas. Specimens were then transferred to individual glass containers with desiccant (molecular sieves 3Å, Sigma-Aldrich Chemie GmbH, Buchs, Switzerland) before being transported to the infrared spectrometer. For two batches of $15 \times 10 \times 3 \text{ mm}^3$ Norway spruce specimens, the time in liquid D₂O was increased to 48 and 72 h, respectively, to study the effect of deuteration time.

Infrared spectroscopic measurements

The infrared spectrum of each specimen was recorded with a Bruker Tensor 27 ATR-FTIR spectrometer (Bruker Optik GmbH, Fällanden, Switzerland) in the spectral range $4000\text{--}400\text{ cm}^{-1}$ with a resolution of 4 cm^{-1} using 64 scans with a total duration of 60 s. Prior to each measurement, the specimen was split approximately in the middle along the LR plane with a sharp razor blade. The freshly cut surface was then quickly put on the diamond ATR crystal and the infrared spectrum recorded. All acquired IR spectra were analysed using OPUS version 7.2 software (Bruker Optik GmbH, Fällanden, Switzerland). Spectra were baseline-corrected using the concave rubber band method (ten iterations, 64 baseline points) and max–min normalised. To avoid contributions from CO_2 vibrations ($2300\text{--}2400\text{ cm}^{-1}$) in the spectra, only half the OD peak area (from 2700 cm^{-1} to peak height around 2500 cm^{-1}) was calculated by numerical integration, see Fig. 1. For two series of $15 \times 10 \times 3\text{ mm}^3$ Norway spruce specimens, the effect of splitting and time before measurement was examined by either not splitting or letting the split specimens be exposed to laboratory conditions (app. 50%RH, $22\text{--}24\text{ }^\circ\text{C}$) for various amounts of time before the spectrum was recorded.

Results and discussion

Table 2 sums up the results for the five major experimental series examining different factors which affected the spectroscopically determined hydroxyl accessibility. Due to loss of specimens during the experiments, for example by

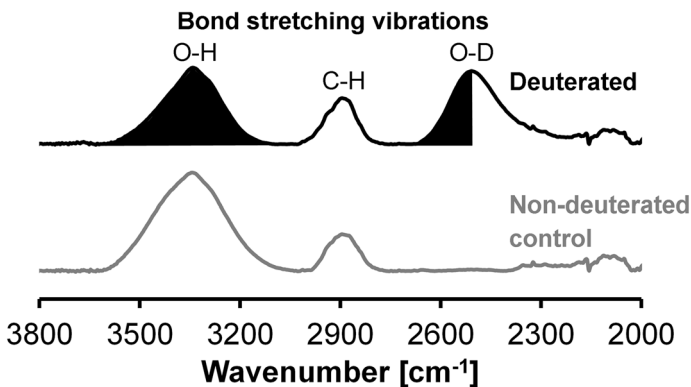


Fig. 1 Average ATR-FTIR spectrum in the range $2000\text{--}3800\text{ cm}^{-1}$ of deuterated Norway spruce after exposure to liquid D_2O and vacuum drying. The *black* part of the O–H and O–D peaks illustrate the areas used for calculating the relative hydroxyl accessibility. Only the area between 2700 cm^{-1} and O–D peak height wavenumber (around 2510 cm^{-1}) was determined to avoid contributions from CO_2 vibrations in the $2300\text{--}2400\text{ cm}^{-1}$ range. The determined half O–D peak area was then doubled for accessibility determinations. Also shown in *grey* is an example of a spectrum of non-deuterated Norway spruce in the range $2000\text{--}3800\text{ cm}^{-1}$

Table 2 Spectroscopically determined hydroxyl accessibility for different, untreated wood species and specimen sizes

Series	Wood specimens	Specimen size	Deuteration time [h]	Batch size	Hydroxyl accessibility [%]
1. Splitting	Norway spruce, split	15 × 10 × 3 mm	24	7	33.4 (6.0)^c
	Norway spruce, not split	15 × 10 × 3 mm	24	5	20.3 (7.6) ^a
2. Deuteration time	Norway spruce, split	15 × 10 × 3 mm	24	7	29.0 (1.4)^b
	Norway spruce, split	15 × 10 × 3 mm	48	6	33.4 (3.5) ^c
	Norway spruce, split	15 × 10 × 3 mm	72	7	33.4 (3.3) ^c
3. Length	Norway spruce, split	15 × 10 × 3 mm	24	3	34.4 (2.5)^c
	Norway spruce, split	30 × 10 × 3 mm	24	3	33.8 (2.7) ^c
4. Thickness	Norway spruce, split	15 × 10 × 1 mm	24	7	21.0 (2.3) ^a
	Norway spruce, split	15 × 10 × 3 mm	24	6	37.8 (1.8)^{c,d,e}
	Norway spruce, split	15 × 10 × 10 mm	24	4	35.0 (1.1) ^c
5. Species	Beech, split	15 × 10 × 3 mm	24	5	37.5 (6.7) ^{c,d}
	Pine sapwood, split	15 × 10 × 3 mm	24	7	41.6 (5.4) ^{e,f}
	Pine heartwood, split	15 × 10 × 3 mm	24	7	39.9 (6.9) ^d
	Norway spruce, split	15 × 10 × 3 mm	24	6	44.3 (4.0)^f

Batches which are not statistically significantly different ($\alpha = 5\%$) based on Duncan's multiple range test have been grouped with similar letters

Highlighted in *bold* are five seemingly identical batches and their accessibilities

uncontrolled breaking during splitting, or too low infrared signal intensity because of inadequate mechanical force pushing the specimen to the ATR crystals, some batches contain less replicates than previously specified. The data for the remaining replicates appear to be in line with previous findings. Thus, the results for Norway spruce are in line with the 36–44% hydroxyl accessibility reported in the literature (Table 1), except for those with the shortest deuteration time in series 2 and the thinnest specimens in series 4. The first of these batches appears to be an outlier, since the four other similar batches highlighted in bold in Table 2 yield significantly higher accessibilities. Thus, it seems that the standard deuteration protocol employed in this study was able to fully deuterate accessible hydroxyls as the accessibility would have otherwise been seen to increase with deuteration time in series 2.

One main concern with the spectroscopic methodology described in this study is water sorption in the time between deuteration and until the infrared spectrum is recorded. This can be avoided when the drying of wet, deuterated specimens is performed in the spectroscopic equipment in a dry purge gas (Altaner et al. 2006; Fackler et al. 2011). However, in the current study specimens are handled in laboratory conditions after vacuum drying. Thus, when specimens are taken out of the vacuum oven and transferred to the spectrometer, water molecules in the surrounding air may be adsorbed by the wood and interact with deuterated hydroxyls. This will cause a decrease in the determined hydroxyl accessibility both

due to re-protonation of hydroxyls, i.e. exchange of D–H, and due to an increase in O–H vibrations from adsorbed water molecules. Splitting of deuterated specimens limits the effect of handling time between vacuum drying and spectrometry by producing a fresh, inner wood surface right before infrared measurements. Thus, it is clear from series 1 that even swift handling of specimens after drying markedly decreases the determined accessibility of non-split specimens. Similarly, Fig. 2 illustrates the determined accessibility of a batch with specimens exposed to laboratory conditions for up to 60 min after splitting. After 10 min of exposure, the accessibility is 30% lower than for the specimen immediately transferred to the spectrometer after splitting.

The risk of re-protonation also plays a role in the recommended specimen geometry. In this study, specimens of 1 mm thickness yielded lower hydroxyl accessibility than specimens of 3 or 10 mm thickness but similar to that of the non-split batch. Increasing the length from 15 to 30 mm did not yield any difference in accessibility. This indicates that the cut surface of 1-mm-thick specimens after splitting may have interacted with water during handling due to the short transport path into the specimen. Moreover, it should be noted that satisfactory splitting in the middle of the specimen is difficult if this is either too small (1 mm thick) or too large (10 mm thick or 30 mm long).

The three wood species examined in this study did show some differences as seen from the grouping in Table 2 based on Duncan's multiple range test. Thus, beech and pine heartwood yielded slightly lower hydroxyl accessibility than pine sapwood and Norway spruce. It is unclear whether this is due to fewer hydroxyls present in beech hemicelluloses (Teleman et al. 2002) than in spruce (Sjöström 1993) and the presence of extractives in pine heartwood. It should, however, be noted that the standard deviation was unexplainably higher in series 1 and 5 than in the other experimental series. No other published studies have examined beech and pine, but

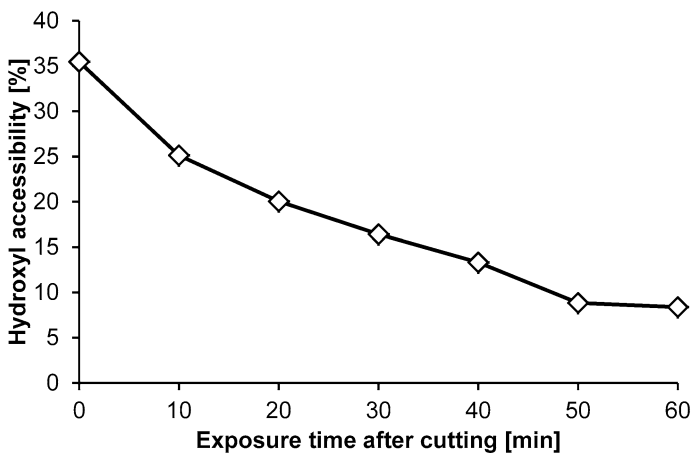


Fig. 2 Spectroscopically determined hydroxyl accessibility for one series of $15 \times 10 \times 3 \text{ mm}^3$ specimens of Norway spruce at different times of exposure to laboratory conditions after splitting in the middle

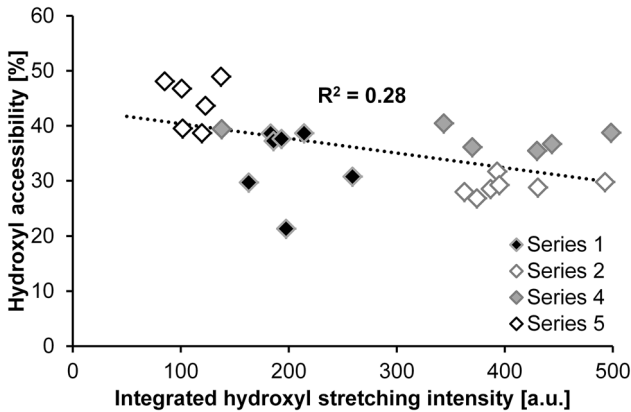


Fig. 3 Relation between spectroscopically determined hydroxyl accessibility and integrated vibrational intensity of hydroxyls (both OH and OD) in deuterated $15 \times 10 \times 3 \text{ mm}^3$ specimens of Norway spruce from four different experimental series

the accessibility determined in this study is within the variability seen for other wood species examined in the literature (Table 1).

One factor which is difficult to control accurately with the ATR-FTIR equipment used in this study is the clamping force used to push the specimen against the ATR crystal. The signal intensity of a given vibration varies with clamping force. However, the ratio between peaks is quite constant for various force levels (Spragg 2011). Thus, after baseline correction and normalisation, the vibrational intensity of the different bonds should be quite similar. Therefore, it is expected that the determined hydroxyl accessibility by ratios of peak areas should be similarly insensitive to clamping force. This can be indirectly seen from the poor correlation in Fig. 3, which shows the relation between determined hydroxyl accessibility and total peak area of hydroxyls (both OH and OD vibrations) for four similar batches. Therefore, differences in hydroxyl accessibility between batches of similarly treated Norway spruce specimens highlighted in bold in Table 2 cannot be explained from variation in clamping force. Differences in annual ring width and thus early-/latewood ratio might explain it, as Chow (1972) found earlywood in Douglas fir to have considerably lower relative hydroxyl accessibility than latewood of the same species. This topic has, however, not been explored further in other studies.

Conclusion

This study illustrates some of the uncertainties involved with the infrared spectroscopically determined hydroxyl accessibility of wood after deuterium exchange. In particular, the risk of re-protonation of deuterated hydroxyls in dry wood specimens during handling is highlighted. Splitting of specimens with adequate dimensions (thickness of at least 3 mm) was shown to give similar

hydroxyl accessibilities for most specimen batches. However, for some of these the determined accessibility deviated inexplicably from the others and results from the literature.

Acknowledgements EET gratefully acknowledges financial support from FP7: People Marie-Curie action COFUND (EMPA POSTDOCS, Project No. 267161).

References

- Altaner C, Apperley DC, Jarvis MC (2006) Spatial relationships between polymers in sitka spruce: proton spin-diffusion studies. *Holzforschung* 60:665–673
- Chow SZ (1972) Hydroxyl accessibility, moisture-content, and biochemical activity in cell-walls of douglas-fir trees. *Tappi* 55:539–544
- Crawford B (1952) Vibrational intensities II. The use of isotopes. *J Chem Phys* 20:977–981
- Englander SW, Downer NW, Teitelbaum H (1972) Hydrogen-exchange. *Annu Rev Biochem* 41:903–924
- Fackler K, Schwanninger M (2011) Accessibility of hydroxyl groups of brown-rot degraded spruce wood to heavy water. *J Near Infrared Spec* 19:359–368
- Fackler K, Stevanic JS, Ters T, Hinterstoisser B, Schwanninger M, Salmén L (2011) FT-IR imaging microscopy to localise and characterise simultaneous and selective white-rot decay within spruce wood cells. *Holzforschung* 65:411–420
- Fernandes AN, Thomas LH, Altaner CM, Callow P, Forsyth VT, Apperley DC, Kennedy CJ, Jarvis MC (2011) Nanostructure of cellulose microfibrils in spruce wood. *Proc Natl Acad Sci USA* 108:E1195–E1203
- Gold V, Satchell DPN (1955) The principles of hydrogen isotope exchange reactions in solution. *Q Rev Chem Soc* 9:51–72
- Hofstetter K, Hinterstoisser B, Salmén L (2006) Moisture uptake in native cellulose—the roles of different hydrogen bonds: a dynamic FT-IR study using deuterium exchange. *Cellulose* 13:131–145
- Kontturi E, Vuorinen T (2009) Indirect evidence of supramolecular changes within cellulose microfibrils of chemical pulp fibers upon drying. *Cellulose* 16:65–74
- Mann J, Marrinan HJ (1956a) The reaction between cellulose and heavy water 1. A qualitative study by infra-red spectroscopy. *T Faraday Soc* 52:481–487
- Mann J, Marrinan HJ (1956b) The reaction between cellulose and heavy water 3. A quantitative study by infra-red spectroscopy. *T Faraday Soc* 52:492–497
- Nara S, Takeo H, Komiya T (1981) Studies on the accessibility of starch by deuteration. *Starch-Stärke* 33:329–331
- Puong LX, Takayama M, Shida S, Matsumoto Y, Aoyagi T (2007) Determination of the accessible hydroxyl groups in heat-treated *styrax tonkinensis* (Pierre) craib ex hartwich wood by hydrogen-deuterium exchange and H-2 NMR spectroscopy. *Holzforschung* 61:488–491
- Popescu CM, Hill CAS, Curling S, Ormondroyd GA, Xie Y (2014) The water vapour sorption behaviour of acetylated birch wood: how acetylation affects the sorption isotherm and accessible hydroxyl content. *J Mater Sci* 49:2362–2371
- Rautkari L, Hill CAS, Curling S, Jalaludin Z, Ormondroyd GA (2013) What is the role of the accessibility of wood hydroxyl groups in controlling moisture content? *J Mater Sci* 48:6352–6356
- Salmén L, Bergström E (2009) Cellulose structural arrangement in relation to spectral changes in tensile loading FTIR. *Cellulose* 16:975–982
- Schmidt M, Gierlinger N, Schade U, Rogge T, Grunze M (2006) Polarized infrared microspectroscopy of single spruce fibers: hydrogen bonding in wood polymers. *Biopolymers* 83:546–555
- Sepall O, Mason SG (1961) Hydrogen exchange between cellulose and water 1. Measurement Access *Can J Chem* 39:1934–1943
- Sjöström E (1993) Wood polysaccharides. In: Sjöström E (ed) *Wood Chemistry*, 2nd edn. Academic Press, San Diego, pp 51–70
- Spragg R (2011) Contact and orientation effects in FT-IR ATR spectra. *Spectroscopy* 26:digital
- Suchy M (2011) Accessibility and enzymatic degradation of native and model cellulose substrates, PhD thesis, Aalto University, Espoo, Finland

- Suchy M, Kontturi E, Vuorinen T (2010a) Impact of drying on wood ultrastructure: similarities in cell wall alteration between native wood and isolated wood-based fibers. *Biomacromol* 11:2161–2168
- Suchy M, Virtanen J, Kontturi E, Vuorinen T (2010b) Impact of drying on wood ultrastructure observed by deuterium exchange and photoacoustic FT-IR spectroscopy. *Biomacromol* 11:515–520
- Sumi Y, Hale RD, Meyer JA, Leopold B, Rånby BG (1964) Accessibility of wood and wood carbohydrates measured with tritiated water. *Tappi* 47:621–624
- Swenson CA (1965) Absolute infrared intensities of HDO in aqueous solution. *Spectrochim Acta* 21:987–993
- Taniguchi T, Harada H, Nakato K (1966) Accessibility of hydroxyl groups in wood. *Mokuzai Gakkaishi* 10:215–220
- Taniguchi T, Harada H, Nakato K (1978) Determination of water-adsorption sites in wood by a hydrogen-deuterium exchange. *Nature* 272:230–231
- Teleman A, Tenkanen M, Jacobs A, Dahlman O (2002) Characterization of O-acetyl-(4-O-methylglucurono)xylan isolated from birch and beech. *Carbohydr Res* 337:373–377
- Thybring EE, Thygesen LG, Burgert I (2017) Hydroxyl accessibility in wood cell walls as affected by drying and re-wetting procedures. *Cellulose* 24:2375–2384
- Venyaminov SY, Prendergast FG (1997) Water (H₂O and D₂O) molar absorptivity in the 1000–4000 cm⁻¹ range and quantitative infrared spectroscopy of aqueous solutions. *Anal Biochem* 248:234–245
- Watanabe A, Morita S, Kokot S, Matsubara M, Fukai K, Ozaki Y (2006) Drying process of microcrystalline cellulose studied by attenuated total reflection IR spectroscopy with two-dimensional correlation spectroscopy and principal component analysis. *J Mol Struct* 799:102–110