

Latest Results on Radiation Tolerance of Diamond Detectors

Conference Paper**Author(s):**

Oh, Alexander; Artuso, Marina; Bachmair, Felix; Bäni, Lukas; Kasieczka, Gregor; [Reichmann, Michael](#) ; RD42 Collaboration

Publication date:

2019

Permanent link:

<https://doi.org/10.3929/ethz-b-000390497>

Rights / license:

[Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International](#)

Originally published in:

PoS: Proceedings of Science 340, <https://doi.org/10.22323/1.340.0597>

Latest Results on Radiation Tolerance of Diamond Detectors

The RD42 Collaboration

A. Oh^{24*}, A. Alexopoulos,³ M. Artuso²⁰, F. Bachmair²⁴, L. Bäni²⁴, M. Bartosik³, J. Beacham¹³, H. Beck²³, V. Bellini², V. Belyaev¹², B. Bentele¹⁹, A. Bes²⁷, J-M. Brom⁷, M. Bruzzi⁴, G. Chiodini²⁶, D. Chren¹⁸, V. Cindro¹¹, G. Claus⁷, J. Collot²⁷, J. Cumalat¹⁹, A. Dabrowski³, R. D'Alessandro⁴, D. Dauvergne²⁷, W. de Boer¹⁰, S. Dick¹³, C. Dorfer²⁴, M. Dünser³, V. Eremin⁶, G. Forcolin²², J. Forneris¹⁵, L. Gallin-Martel²⁷, M-L. Gallin-Martel²⁷, K.K. Gan¹³, M. Gastal³, M. Goffe⁷, J. Goldstein¹⁷, A. Golubev⁸, A. Gorišek⁹, E. Grigoriev⁸, J. Grosse-Knetter²³, A. Grummer²¹, M. Guthoff³, I. Haughton²², B. Hiti⁹, D. Hits²⁴, M. Hoferkamp²¹, T. Hofmann³, J. Hosslet⁷, J-Y. Hostachy²⁷, F. Hügging¹, C. Hutton¹⁷, J. Janssen¹, H. Kagan¹³, K. Kanxheri²⁸, G. Kasieczka²⁴, R. Kass¹³, F. Kassel¹⁰, M. Kis⁵, G. Kramberger⁹, S. Kuleshov⁸, A. Lacoste²⁷, S. Lagomarsino⁴, A. Lo Giudice¹⁵, E. Lukosi²⁵, C. Maazouzi⁷, I. Mandic⁹, C. Mathieu⁷, M. Menichelli²⁸, M. Mikuž⁹, A. Morozzi²⁸, J. Moss²⁹, R. Mountain²⁰, S. Murphy²², P. Olivero¹⁵, D. Passeri²⁸, H. Pernegger³, R. Perrino²⁶, F. Picollo¹⁵, M. Pomorski¹¹, R. Potenza², A. Quadt²³, A. Re¹⁵, M. Reichmann²⁴, G. Riley²⁵, S. Roe³, D. Sanz²⁴, M. Scaringella⁴, C.J. Schmidt⁵, S. Schnetzer¹⁴, S. Sciortino⁴, A. Scorzoni²⁸, S. Seidel²¹, L. Servoli²⁸, D.S. Smith¹³, B. Sopko¹⁸, V. Sopko¹⁸, S. Spagnolo²⁶, S. Spanier²⁵, K. Stenson¹⁹, R. Stone¹⁴, C. Sutura², A. Taylor²¹, M. Traeger⁵, D. Tromson¹¹, W. Trischuk¹⁶, C. Tuve², J. Velthuis¹⁷, N. Venturi³, E. Vittone¹⁵, S. Wagner¹⁹, R. Wallny²⁴, J.C. Wang²⁰, J. Weingarten²³, C. Weiss³, N. Wermes¹, M. Yamouni²⁷, M. Zavrtanik⁹

¹Universität Bonn, Bonn, Germany; ²INFN/University of Catania, Catania, Italy; ³CERN, Geneva, Switzerland; ⁴INFN/University of Florence, Florence, Italy; ⁵GSI, Darmstadt, Germany; ⁶Ioffe Institute, St. Petersburg, Russia; ⁷IPHC, Strasbourg, France; ⁸ITEP, Moscow, Russia; ⁹Jožef Stefan Institute, Ljubljana, Slovenia; ¹⁰Universität Karlsruhe, Karlsruhe, Germany; ¹¹CEA-LIST Technologies Avancées, Saclay, France; ¹²MEPHI Institute, Moscow, Russia; ¹³The Ohio State University, Columbus, OH, USA; ¹⁴Rutgers University, Piscataway, NJ, USA; ¹⁵University of Torino, Torino, Italy; ¹⁶University of Toronto, Toronto, ON, Canada; ¹⁷University of Bristol, Bristol, UK; ¹⁸Czech Technical Univ., Prague, Czech Republic; ¹⁹University of Colorado, Boulder, CO, USA; ²⁰Syracuse University, Syracuse, NY, USA; ²¹University of New Mexico, Albuquerque, NM, USA; ²²University of Manchester, Manchester, UK; ²³Universität Göttingen, Göttingen, Germany; ²⁴ETH Zürich, Zürich, Switzerland; ²⁵University of Tennessee, Knoxville, TN, USA; ²⁶INFN-Lecce, Lecce, Italy; ²⁷LPSC-Grenoble, Grenoble, France; ²⁸INFN-Perugia, Perugia, Italy; ²⁹California State University, Sacramento, CA, USA.

The 39th International Conference on High Energy Physics (ICHEP2018)
4-11 July, 2018
Seoul, Korea

*Corresponding author. Email:alexander.oh@manchester.ac.uk

At present most experiments at the CERN Large Hadron Collider (LHC) are planning upgrades in the next 5-10 years for their innermost tracking layers as well as luminosity monitors to be able to take data as the luminosity increases and CERN moves toward the High Luminosity-LHC (HL-LHC). These upgrades will most likely require more radiation tolerant technologies than exist today. As a result this is one area of intense research, and Chemical Vapour Deposition (CVD) diamond is one such technology. CVD diamond has been used extensively in beam condition monitors as the innermost detectors in the highest radiation areas of all LHC experiments. This talk describes the preliminary radiation tolerance measurements of the highest quality polycrystalline CVD material for a range of proton energies and neutrons obtained with this material with the goal of elucidating the issues that should be addressed for future diamond based detectors. The talk presents the evolution of various semiconductor parameters as a function of dose.

1. Introduction

The innermost tracking detector systems at Hadron Collider Experiments of the next generation will face a challenging radiation environment. Synthetic diamond from a chemical vapour deposition process (CVD) has been investigated as a promising alternative candidate to silicon due to its nearly twice higher atomic displacement energy and high intrinsic resistivity.

The RD42 collaboration has explored the radiation tolerance of single (sCVD) and polycrystalline CVD diamond (pCVD) with protons and neutrons at energy ranges relevant to the particle spectra encountered at the Large Hadron Collider (LHC), up to a particle fluence required by the high luminosity upgrade of the LHC (HL-LHC) [1]. In the following the characterisation method of radiation tolerance will be discussed (Section 2) and the results of protons and neutron irradiations on pCVD and sCVD will be summarised (Section 3).

2. Characterisation of Radiation Tolerance

Diamond samples were characterised before and after irradiation by measuring the charge signal with 120 GeV/c protons in the H6 beam line at the CERN Super-Proton-Synchrotron (SPS). The samples were typically sized 5 mm × 5 mm or 10 mm × 10 mm and metallized with a segmented strip electrode structure on the front-side and a continuous electrode on the back-side. The strips were wire-bonded to a VA2 readout chip for charge integration and shaping the signal; the electronic noise was about 80 electrons. Before testing the sensors they were exposed to beta particles from a ⁹⁰Sr source to fill charge traps. The detectors were tested at an electric field strength of 1 V μm⁻¹ and 2 V μm⁻¹. A beam telescope predicted the track position at the diamond sensor with a resolution of 4 μm. The charge signal was built from the sum of the highest two strip cluster within 10 strips around the predicted track position.

A 120 GeV/c proton is a minimum ionising particle (MIP) and will create on average 36 electron-hole pairs per micrometer in diamond. The measured MIP signal Q_m is commonly expressed in terms of the charge collection distance defined as $\delta = \frac{Q_m}{36 e \mu\text{m}^{-1}}$. The charge signal is reduced by active traps reducing the life-time of the electrons and holes. The life time τ is proportional to the "Schubweg" $\lambda \propto \frac{1}{\tau}$ and since production of traps by radiation is proportional to the

fluence the radiation damage can be parameterised as

$$\frac{1}{\lambda} = \frac{1}{\lambda_0} + k_\lambda \Phi \quad (2.1)$$

with λ_0 representing the un-irradiated state, and the damage constant k_λ describing the introduction of additional traps with the fluence Φ . The MIP signal efficiency ε , charge collection distance δ and Schubweg are related by

$$\varepsilon = Q_m/Q_{MIP} = \delta/d = 2\frac{\lambda}{d}\left(1 - \frac{\lambda}{d}(1 - e^{-d/\lambda})\right) \quad (2.2)$$

with d the thickness of the detector.

A typical signal spectrum obtained with 120 GeV/c protons with single crystal CVD diamond material is shown in Figure 1a. The spectra show the typical Landau shape for MIP signals, the degradation of the signal with proton fluence is clearly visible. In Figure 1b the dependence of the ratio, f , of FWHM to most probable value is compared for single crystal and polycrystalline CVD diamond. The value of f is decreasing for pCVD while sCVD shows a slow rise of f with proton fluence, indicating a common value at high proton fluence. The resistivity of diamond is not significantly changed with irradiation fluence [2], and due to the large band shows also no significant dependence with temperature at room temperatures or below [2].

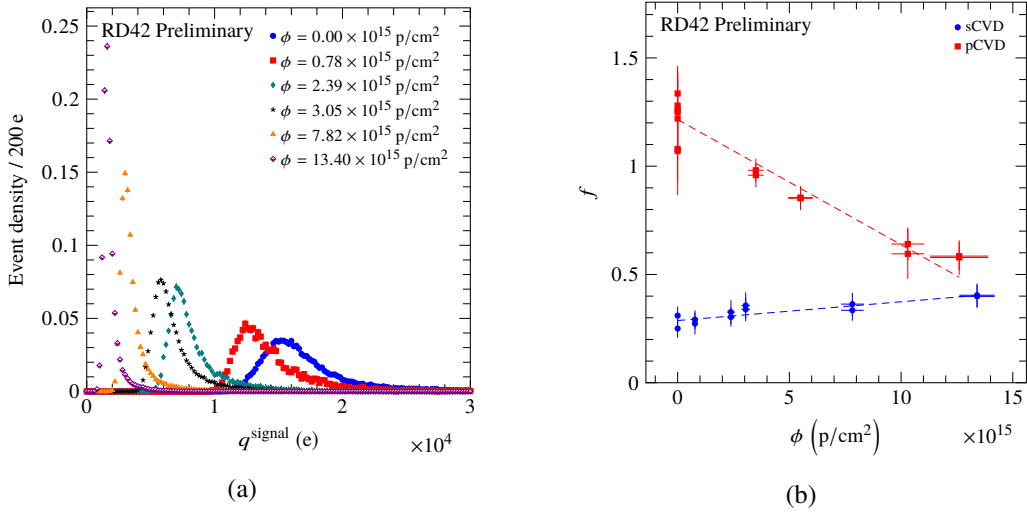


Figure 1: MIP signal spectra of single crystal diamond detectors at different 800 MeV proton fluences (a), and ratio of FWHM to the most probable value of the MIP signal for single crystal and polycrystalline CVD diamond (b) [3].

From the measured charge Q_m the Schubweg λ can be determined by solving equation 2.2. The linear dependence of the inverse of lambda, $1/\lambda$, with proton fluence can be seen in Figure 2a. The slope of a linear fit to these data in $1/\lambda$ allows to extract the damage constant k_λ from equation 2.1. The gradient of $1/\lambda$ is comparable for different sCVD and pCVD diamond samples while the variations in offset are due to the initial material conditions and are captured by the λ_0 term in equation 2.1. This indicates that the simple model for radiation damage parametrises well the damage in pCVD and sCVD diamond.

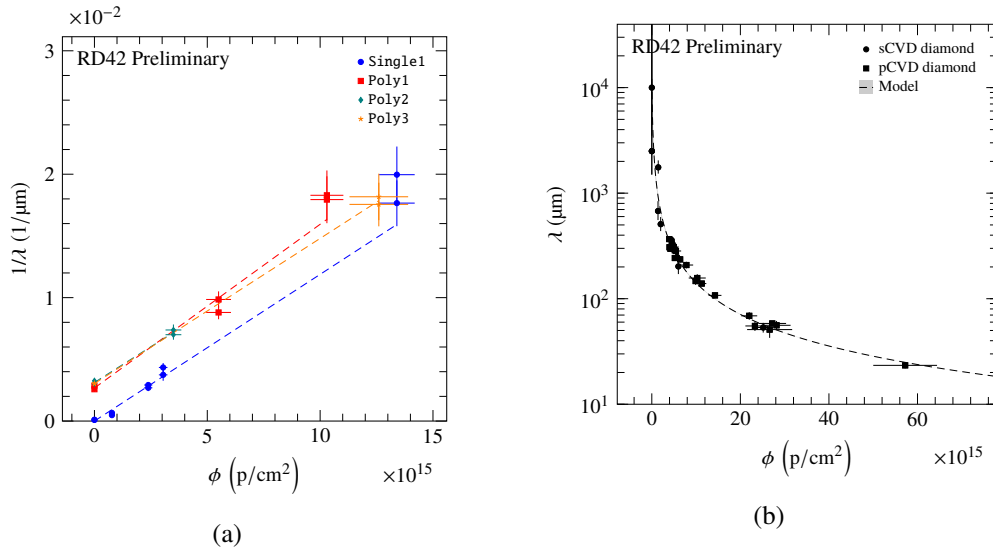


Figure 2: Measurements of inverse Schubweg as a function of 800 MeV protons fluence for sCVD and pCVD samples for two polarities with statistical and systematic error added in quadrature [3] (a). Measured Schubweg as a function of 24 GeV protons equivalent fluence compared to the radiation damage model (dashed curve) [3] (b).

3. Summary of Results

A series of irradiations of sCVD and pCVD diamonds and subsequent characterisation in test-beams has been conducted. Samples have been irradiated with 25 MeV to 24 GeV protons, up to maximum fluence of $1.3 \cdot 10^{16} \text{ p cm}^{-2}$ and with fast neutrons corresponding to an energy range of 1 MeV to 10 MeV up to a fluence of $1.3 \cdot 10^{16} \text{ n cm}^{-2}$.

From this data-set the damage constants k as a function of particle type and energy were extracted. Although we are not in a position at this time to quote the absolute values of k , current preliminary values indicate they are 2-4 times lower in diamond than in silicon. The initial signal is lower in diamond compared to silicon, however the low leakage current and low k factors puts diamond ahead of silicon for fluence above 10^{15} particles cm^2 in terms of signal-to-noise ratio for a typical HL-LHC pixel detector application [4].

References

- [1] G. Apollinari, O. Brüning, T. Nakamoto and L. Rossi, *High Luminosity Large Hadron Collider HL-LHC*, *CERN Yellow Report* (2015) 1 [1705.08830].
- [2] RD42 collaboration, S. Seidel, *Recent results on diamond radiation tolerance*, *JINST* **9** (2014) C01013.
- [3] L. Baeni, *Top Quarks and Diamonds*, Ph.D. thesis, ETH, Zuerich, 2017. <http://doi.org/10.3929/ethz-a-010748643>.
- [4] J.-W. Tsung, M. Havranek, F. Hügging, H. Kagan, H. Krüger and N. Wermes, *Signal and noise of diamond pixel detectors at high radiation fluences*, *JINST* **7** (2012) P09009.